



The Application of Mesoporous ZSM-5 Zeolite in the ULSD Catalysts

Liu L^{1*}, Tang TD², Guo R¹, Yang CM¹, Duan WY¹, Sun J¹ and Yao YH¹

¹Dalian Research Institute of Petroleum and Petrochemical, SINOPEC, China

²School of Petrochemical Engineering, Changzhou University, China

***Corresponding author:** Liu Li, Dalian Research Institute of Petroleum and Petrochemical, SINOPEC, Dalian, 116045, China, Tel: 0411-39699436/17304110626; Email: liuli.fshy@sinopec.com

Mini Review

Volume 4 Issue 4

Received Date: September 11, 2020

Published Date: October 05, 2020

DOI: 10.23880/ppej-16000236

Abstract

The mesoporous ZSM-5 zeolite containing MoCoP/Al₂O₃ catalyst (C12-ZSM5) with the mixture of Al₂O₃ and mesoporous ZSM-5 zeolite as carrier was synthesized. The catalytic performance of C12-ZSM5 catalyst was evaluated by the hydrodesulfurization (HDS) of different diesel feedstock. The carriers and catalysts were characterized by N₂ adsorption-desorption, pyridine-FTIR, X-ray diffraction (XRD) and CO in-situ FTIR (CO-FTIR) techniques. Results showed that mesoporous ZSM-5 can improve the acidity of the catalyst and increase the number of MoCoS active phases. The C12-ZSM5 catalyst had low HDS and HDN activity, because the acidic sites of mesoporous ZSM-5 were easily occupied by nitrogen compounds. The HDS activity of C12-ZSM5 catalyst was fully exploited by using graded packing technology, the sulfur content of product oil was 5.9 ng/μL. The relative HDS activity of C12-ZSM5 catalyst is 1.47 times that of FHUDES-8 catalyst.

Keywords: ZSM-5 zeolite; Hydrodesulfurization (HDS); Catalysts; Ultra-low sulfur diesel (ULSD)

Introduction

The requirements that the diesel must meet in transport applications have been more stringent in the last decade. The sulfur concentration, a major impurity in crude oil, has been limited to no more than 10 ppm in many countries. There are several methods to product ultra-low sulfur diesel (ULSD), such as feedstock or crude oil selection, reducing the final point of feedstock, adding kerosene distillate, increasing operating temperature, utilizing the higher activity catalyst systems, building new hydrotreating units and so on. The most economical method is to use higher activity hydrodesulfurization (HDS) catalyst system [1].

The novel supports, active phases, promoters, or additives are used to improve the performance of the HDS catalyst. MoS₂ supported on alumina is promoted with Co or Ni [2]. An alternative material as carrier can greatly improve

the HDS activity. A diversity of materials has been used as carriers, i.e., carbon [3], mixed oxides [4], and mesostructured silicas such as MCM-4 [5] and SBA-15 [6]. In our work, we apply mesoporous ZSM-5 in the ULSD catalysts.

Experimental

Mesoporous ZSM-5 (Meso-ZSM-5) was synthesized from an aluminosilicate gel with mesoporous template. The mixture of ZSM-5, γ-Al₂O₃ and additives in a definite ratio was extracted, and then drying and calcination to produce supports. The carriers are referred as DX-ZSM5 (X= 25, 15, 12, 10, 8, 0) where X is the weight% of ZSM-5. The contrast support (D12-typical ZSM5) was prepared, and the typical ZSM-5 zeolite was synthesized according to the procedure reported in literature [7].

Mo-Co oxide precursors were prepared by impregnation

of aqueous solutions of ammonium heptamolybdate and cobalt nitrate on the supports. The supports were treated in air at 100 °C for 6 h and then at 400°C for 3 h. The compositions were 18 wt.% MoO₃ and 3 wt.% CoO for the catalysts. FHUDES-8 catalyst was developed by Dalian Research Institute of Petroleum and Petrochemical, and the active metals were Mo and Ni.

The supports and catalysts were characterized by BET, SEM, IR, H₂-TPR and CO-FTIR. The HDS activity of the catalysts was evaluated using two types of straight-run diesel as raw oil. The sulfur and nitrogen concentrations of raw oil were 0.73 wt. %, 58.2 ppm and 1.42 wt. %, 389 ppm, respectively.

Results and Discussion

Figure 1 showed the pore distribution of the Meso-ZSM-5 and typical ZSM-5. The most probable aperture of Meso-ZSM-5 was 2nm and 20nm. Compared with typical ZSM-5, the mesoporous structure of Meso-ZSM-5 was obvious. The 100nm small particles accumulated to form 5000nm large particles in the Meso-ZSM-5 (SEM result), and there were many intercrystalline pores between the small particles, which provided more space and active sites for the reaction comparing with typical ZSM-5.

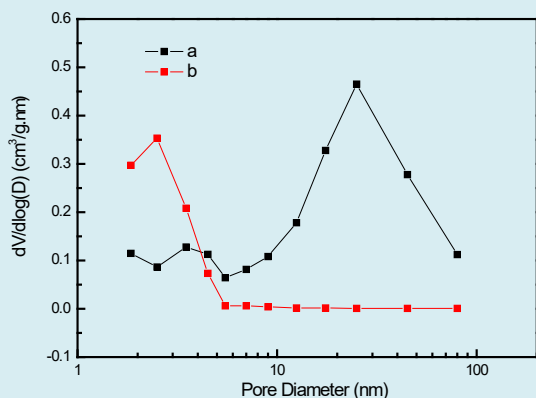


Figure 1: The pore distribution of meso-ZSM-5 (a) and typical ZSM-5(b).

The pore volume of DX-ZSM5 carriers decreased with the increase of Meso-ZSM-5, because the pore volume of Meso-ZSM-5 was smaller than that of Al₂O₃. The CO-FTIR results showed that the ratio of CoMoS active sites firstly increased and then decreased with the increase of Meso-ZSM-5. The CoMoS active sites of catalyst with 12% Meso-ZSM-5 content (C12-ZSM5) were the highest, which indicated the catalyst

had best HDS activity.

The relative HDS activity of different catalysts was showed in Figure 2. The results indicated that the HDS activity of catalysts firstly increased and then decreased with the increase of Meso-ZSM-5, and the HDS activity of C12-ZSM5 was the best. Comparing with C0-ZSM5 (Al₂O₃ support), the relative HDS activity of C12-ZSM5 and C12-typical-ZSM5 was 126% and 94%, respectively, which indicated that the Meso-ZSM-5 could greatly improve the HDS activity.

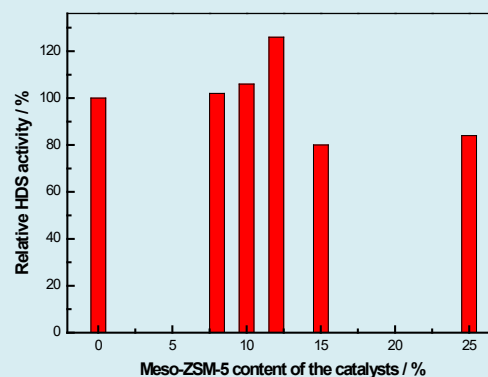


Figure 2: The relative HDS activity of catalysts.

The Meso-ZSM-5 could be poisoned by the nitrides of raw oil, so we adopted the FHUDES-8 (Mo-Ni) / C12-ZSM5 catalysts combination. The results showed that the sulfur content of product was 5.5 ppm for the FHUDES-8 (Mo-Ni) / C12-ZSM5 catalysts combination, while 10.7 ppm for FHUDES-8 catalyst at the same operation conditions. The relative HDS activity of FHUDES-8 (Mo-Ni) / C12-ZSM5 catalysts combination was 1.47 times higher than that of FHUDES-8 catalyst.

Conclusions

The HDS activity of catalysts firstly increased and then decreased with the increase of Meso-ZSM-5, and the HDS activity of the catalyst with 12% Meso-ZSM-5 (C12-ZSM5) was the best. The relative HDS activity of FHUDES-8 (Mo-Ni) / C12-ZSM5 catalysts combination was 1.47 times higher than that of FHUDES-8 catalyst.

References

1. Fang XC, Guo R, Yang CM (2013) The development and application of catalysts for ultra-deep hydrodesulfurization of diesel. Chinese Journal of Catalysis 34(1): 130-139.

2. Marina E, Roel P (2006) The role of Ni and Co promoters in the simultaneous HDS of dibenzothiophene and HDN of amines over Mo/ γ -Al₂O₃ catalysts. *Journal of Catalysis* 241(1): 162-172.
3. Nikulshin PA, Salnikov VA, Mozhaev AV, Minaeva PP, Kogan VM, et al. (2014) Relationship between active phase morphology and catalytic properties of the carbon-alumina-supported Co(Ni)Mo catalysts in HDS and HYD reactions. *Journal of Catalysis* 309: 386-396.
4. Murali Dhar GB, Srinivas N, Rana MS, Manoj Kumar, Maity SK (2003) Mixed oxide supported hydrodesulfurization catalysts-a review. *Catalysis Today* 86(1-4): 45-60.
5. Wang AJ, Wang Y, Toshiaki K, Chen Y, Ishihara A, et al. (2002) Hydrodesulfurization of Dibenzothiophene over Siliceous MCM-41-Supported Catalysts: II. Sulfided Ni-Mo Catalysts. *Journal of Catalysis* 210(2): 319-327.
6. Huirache-Acuña R, Zepeda TA, Rivera-Muñoz EM, Nava CVR, Loricera CV, et al. (2015) Characterization and HDS performance of sulfided CoMoW catalysts supported on mesoporous Al-SBA-16 substrates. *Fuel* 149: 149-161.
7. Yu QY, Zhang L, Guo R, Jin Sun, Wenqian Fu, et al. (2017) Catalytic performance of CoMo catalysts supported on mesoporous ZSM-5 zeolite-alumina composites in the hydrodesulfurization of 4,6-dimethyldibenzothiophene. *Fuel Processing Technology* 159: 76-87.

